




Compressive strength gain of Five Star Repair Concrete at various temperatures


Temperature = 5°C					
1 day	2 days	3 days	7 days	14 days	28 days
1.08	12.04	23.97	45.40	59.27	65.77



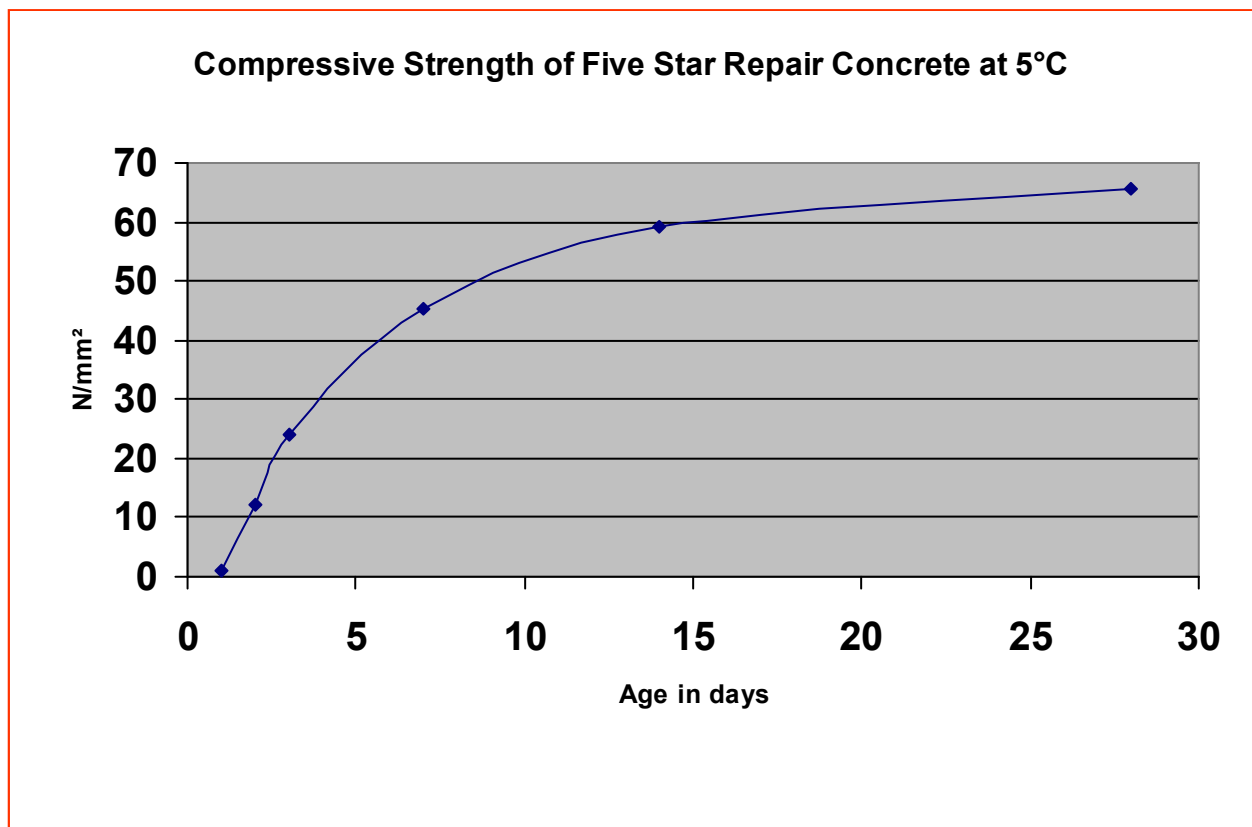

Compressive strength gain of Five Star Repair Concrete at various temperatures


Temperature = 10°C					
1 day	2 days	3 days	7 days	14 days	28 days
1.19	16.81	27.95	42.78	61.23	63.20

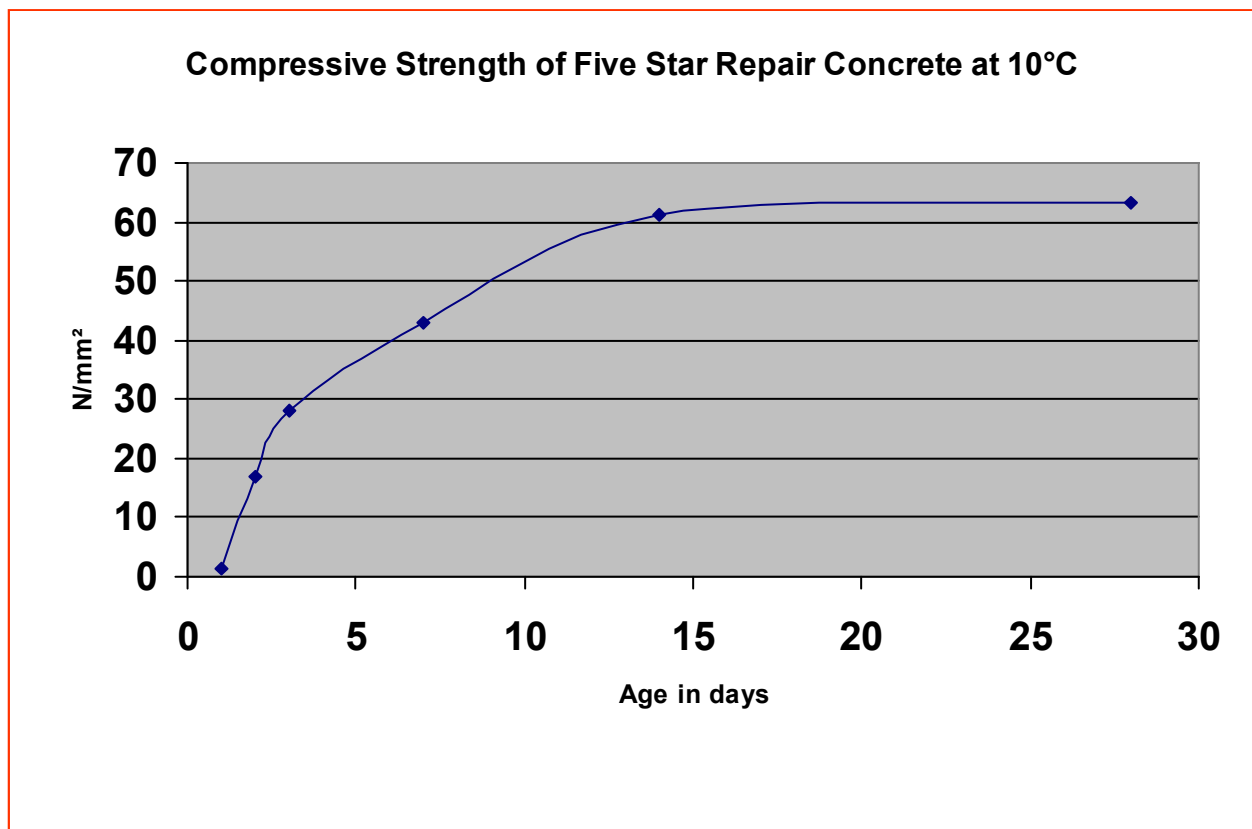



Compressive strength gain of Five Star Repair Concrete at various temperatures

Temperature = 15°C					
1 day	2 days	3 days	7 days	14 days	28 days
0.74	19.25	31.56	46.21	53.57	63.13

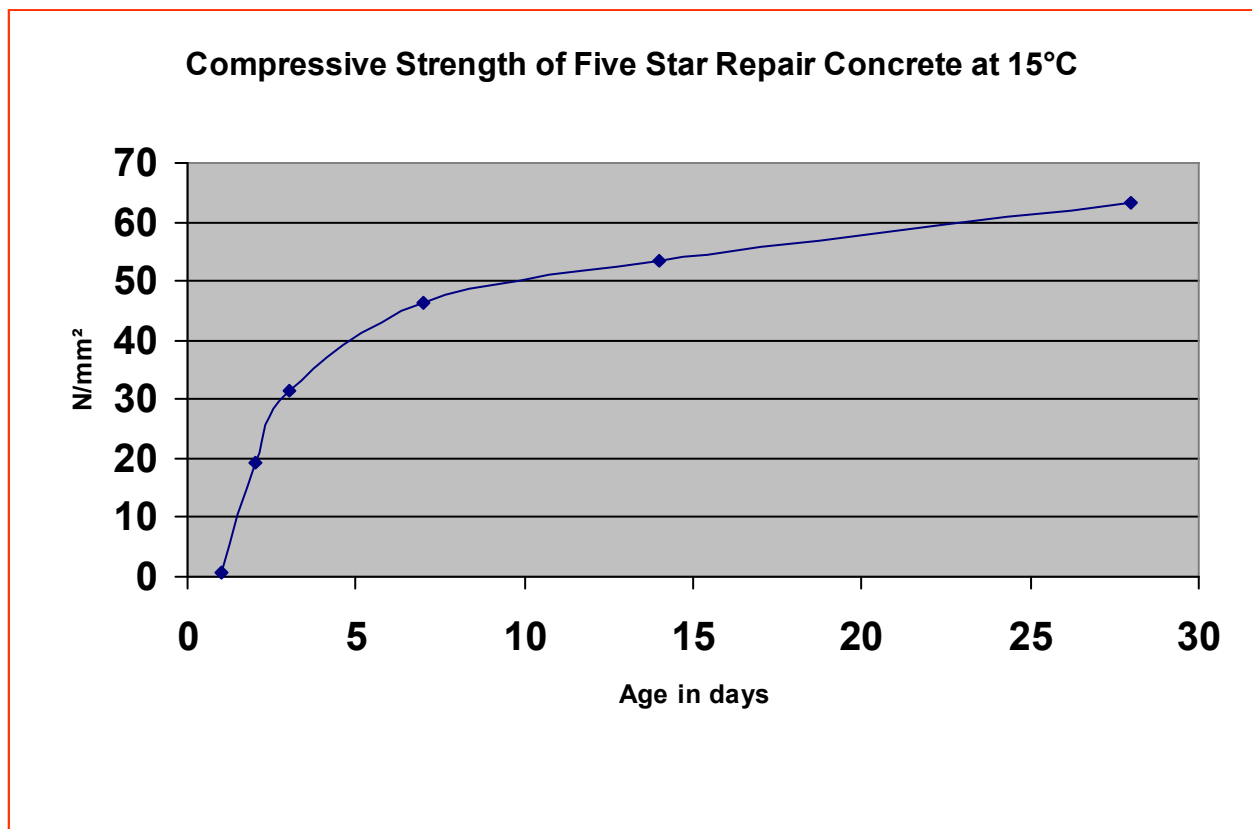



Compressive strength gain of Five Star Repair Concrete at various temperatures

Temperature = 20°C					
1 day	2 days	3 days	7 days	14 days	28 days
26.67	34.41	50.46	52.83	57.63	64.67

